



Proton Diffusion in the Ni/YSZ Electrode of a Solid Oxide Cell

Jensen, Sren; Hauch, Anne; Chorkendorff, Ib; Jacobsen, Torben; Mogensen, Mogens Bjerg

Published in:
Electrochemical Society. Meeting Abstracts (Online)

Publication date:
2006

Document Version
Publisher's PDF, also known as Version of record

[Link back to DTU Orbit](#)

Citation (APA):
Jensen, S., Hauch, A., Chorkendorff, I., Jacobsen, T., & Mogensen, M. B. (2006). Proton Diffusion in the Ni/YSZ Electrode of a Solid Oxide Cell. *Electrochemical Society. Meeting Abstracts (Online)*, Abstract 843.

General rights

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

- Users may download and print one copy of any publication from the public portal for the purpose of private study or research.
- You may not further distribute the material or use it for any profit-making activity or commercial gain
- You may freely distribute the URL identifying the publication in the public portal

If you believe that this document breaches copyright please contact us providing details, and we will remove access to the work immediately and investigate your claim.

Proton diffusion in the Ni/YSZ electrode of a Solid Oxide Cell

*[†]S. H. Jensen, *[#]A. Hauch, and [†]I. Chorkendorff,
[#]T. Jacobsen, *M. Mogensen

*Materials Research Department, Risø National Laboratory, DK-4000 Roskilde, Denmark
[†] Dept. of Physics, Technical University of Denmark, DK-2800 Lyngby, Denmark
[#] Dept. of Chemistry, Technical University of Denmark, DK-2800 Lyngby, Denmark

A Solid Oxide Fuel Cell (SOFC) can be used as a Solid Oxide Electrolyser Cell (SOEC) for high temperature electrolysis of H₂O and CO₂ into H₂ and CO (syngas). Syngas can be catalyzed into various types of hydrocarbon energy carriers. This is highly interesting for synthetic fuel production due to a possibility of high efficiencies and low costs.

Unfortunately, under certain conditions, the cells show a paprtial passivation during the first 100 hours of operation, see figure 1. In some cases the cell performance subsequently recovers slowly over time. Electrochemical impedance spectroscopy (EIS) combined with gas changes shows that the passivation happens on the Ni/YSZ-electrode.

During this initial period of SOEC operation, the Ni/YSZ-electrode EIS response builds up as shown in figure 2. The 45 degree straight line at high frequency ending in a semicircle at low frequency is the response from diffusion across a finite Nerstian diffusion layer.¹ Comparison of the increase in polarization resistance (R_p) with the corresponding decrease in summit frequency indicates that the increase in R_p is due to an increase in a diffusion length, δ .

Isotope experiments (H → D) after operation in SOEC mode results in a decrease in summit frequency corresponding to 34% increase in diffusion coefficient. The classical diffusion theory predicts an increase of 41%.

By assuming the observed diffusion process is proton diffusion in the bulk of YSZ² one finds diffusion lengths of the order of 40 nm before SOEC operation and 400 nm after. Impurity rim ridges at the three phase boundary (TPB) with sizes up to 3 μ m has been observed on Ni-point electrodes on YSZ.³

The above findings points toward a model for steam reduction as shown in figure 3. Steam is adsorbed on the YSZ surface where it is reduced. Protons migrate to the Ni-surface where they desorb as H₂. The observed increase in R_p is due to a build up of impurities at the TPB.

Acknowledgement

The authors would like to acknowledge NEFP and Hi2H2 (EU contract no. FP6-503765) for financial support, and the entire Risø National Laboratory SOFC group for assistance in this work.

References

1. Jacobsen, T. & West, K. Diffusion Impedance in Planar, Cylindrical and Spherical-Symmetry.

Electrochimica Acta **40**, 255-262 (1995).

2. Wagner, C. Solubility of Vapor in ZrO₂-Y₂O₃ Mixed Crystals. *Berichte der Bunsen-Gesellschaft fur Physikalische Chemie* **72**, 778 (1968)

3. Jensen, K. V., Wallenberg, R., Chorkendorff, I. & Mogensen, M. Effect of impurities on structural and electrochemical properties of the Ni-YSZ interface. *Solid State Ionics* **160**, 27-37 (2003).

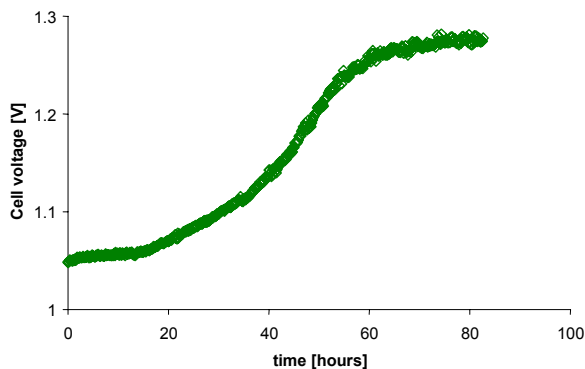


Figure 1. Cell voltage during SOEC operation. Test conditions were 750 °C, -0.25 A/cm², 70% H₂O + 30% H₂ to the Ni-electrode and O₂ to the LSM-electrode.

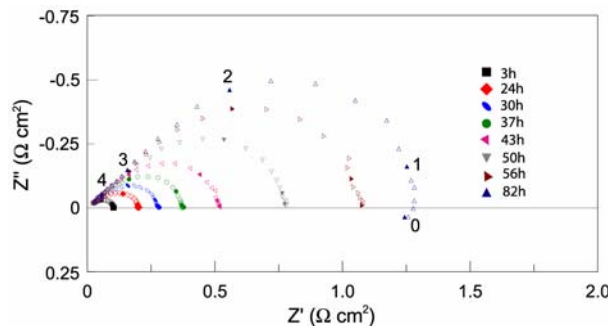


Figure 2. Nyquist plot of the Ni/YSZ-electrode EIS response obtained during SOEC operation. Test conditions are given in figure 1. Time after onset of SOEC operation is given in hours (h) Numbers on figure refer to frequency decade for the closed symbols. Note the decrease in summit frequency.

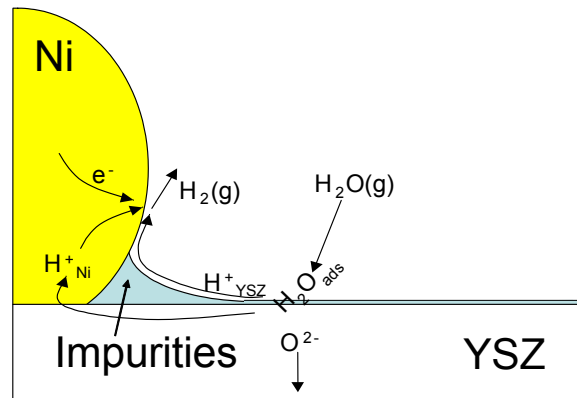


Figure 3. Impurities build up at the TPB and increase the diffusion length for protons migrating from the YSZ to the Ni.